

Therefore, the heat-treatment results have indicated the following features of Ni-22 Cr and Ni-30 Cr prior to shock deformation :

- (1) There is an anomalous increase in resistivity with temperature.
- (2) There is an equilibrium domain size with LRO within the domains.
- (3) Ordering occurs through the establishment of antiphase domains with an equilibrium concentration of vacancies within the domains.
- (4) The processes attributed to (1) and (2) operate in parallel with different temperature responses.

3.2. Shock Deformation Experiments

Specimens of Ni-22 Cr and Ni-30 Cr were shock loaded after three types of initial heat treatments :


- (a) water quench from 1250°C ;
- (b) furnace cool from 1250°C ; and
- (c) water quench from 1250°C followed by isothermal annealing at 350°C for 3 hours.

Table 2. Shock induced resistivity changes

Alloy	Heat treatment	Shock pressure (kbar)	$\Delta\rho/\rho_0$
Ni-22 Cr	Furnace cool (FC) 1250°C	90	-0.0050
		200	-0.0080
		300	-0.0600
Ni-30 Cr	FC, 1250°C	90	-0.0040
		200	-0.0090
		300	-0.0421
Ni-22 Cr	Quenched (Q), 1250°C	90	-0.0001
		200	-0.0003
		300	-0.0004
Ni-30 Cr	Q, 1250°C	300	-0.0003
Ni-22 Cr	Q, 1250°C ; A, 350°C	90	-0.0048
		200	-0.0063
		300	-0.0530
Ni-30 Cr	Q, 1250°C ; A, 350°C	90	-0.0070
		200	-0.0075
		300	-0.0350

Table 2 and fig. 6 summarize the shock-induced changes in electrical resistivity of Ni-22 Cr and Ni-30 Cr. It is noted that shock loading at 300 kbar generally destroys the ordered state for (1) the furnace cooled specimens and (2) the quenched and re-annealed specimens. The resistivity of the disordered (quenched) alloys was found to decrease continuously with shock pressure. This change in resistivity is surprising since the

Fig. 6

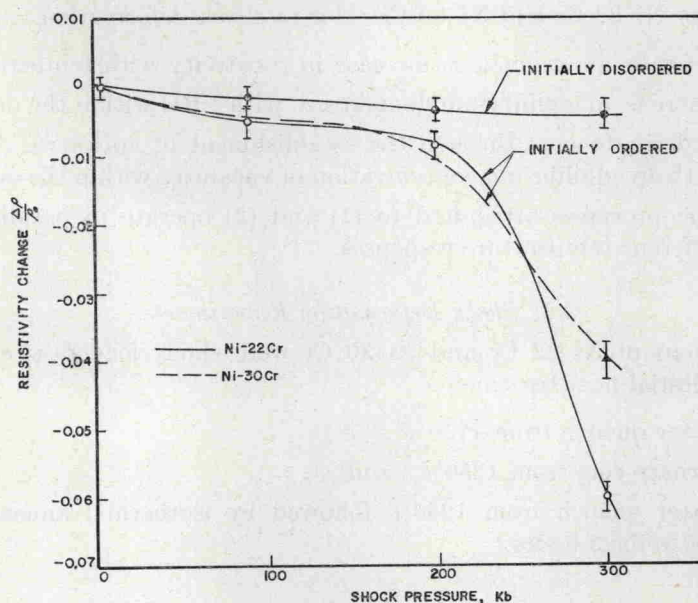

Effect of shock pressure on the resistivity of Ni-22 Cr and Ni-30 Cr.

shock deformation of a random solid solution is expected to increase the resistivity by producing a high density of point defects. The decrease in resistivity may be an indication that the quench had not completely destroyed K-state.

Figure 7 shows the effect of isothermal annealing on Ni-22 Cr furnace cooled specimens, shock loaded at 300 kbar. In the temperature range of 300°–400°C, within which the K-state is intensively formed (Nordheim and Grant 1953), the resistivity of the furnace cooled-shock loaded specimens attained their pre-shock value. The increase in resistivity during annealing, which is highly irregular for other alloys is further evidence that some type of order occurred. As shown in fig. 7, a similar effect was observed for the Ni-30 Cr alloy. It is apparent that the principal effect of shock deformation on furnace cooled Ni-22 Cr and Ni-30 Cr alloys is not so much in the accumulation of shock induced defects as in the transition from an ordered to a random solid solution. The subsequent annealing of the furnace cooled, shock loaded specimens forms a state of order which may be similar to K-state.

Isothermal annealing of the quenched-shock loaded specimens resulted in the recovery of K-state and shock induced point defects. This result is expected since the effect of shock deformation of a random solid solution is the accumulation of point defects and dislocations. In the temperature range of 400°–500°C the resistivity of the quenched-shock loaded specimens approached the resistivity of K-state. Shock deformation does not inhibit the formation of K-state in Ni-Cr alloys.