

(5) THE INFLUENCE OF PRESSURE ON THE MAGNETIC PROPERTIES OF ZINC SINGLE CRYSTALS AT LOW TEMPERATURES


I. M. DMITRENKO, B. I. VERKIN, and B. G. LAZAREV

Physico-Technical Institute, Academy of Sciences, Ukrainian S.S.R.

Submitted to JETP editor April 5, 1957

J. Exptl. Theoret. Phys. (U.S.S.R.) 33, 287-289 (July, 1957)

(6) AN investigation of the magnetic properties of metals at low temperatures and under pressure is of interest in connection with the possible effect of the pressure on the structure of the electron energy spectrum in the metal. For metals in which the de Haas-van Alphen effect is observed, such an investigation is of particular interest in connection with the presence of different types of binding forces between the atoms of the lattice. It is possible that this may explain one of the fundamental magnetic properties of this group of metals, namely the presence of anomalously small groups of electrons.¹

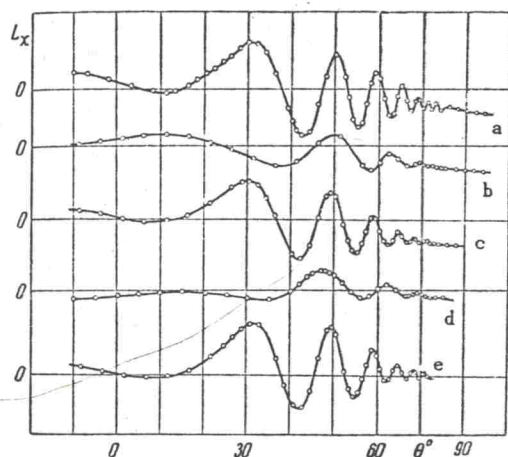

(7) FIG. 1. The torque acting on a zinc crystal in a homogeneous magnetic field as a function of the angle θ between the field vector and the hexagonal crystal axis; $T = 4.2^\circ \text{ K}$, $H = 8400$ oersteds. (a) $P = 0 \text{ kg/cm}^2$; (b) $P \sim 1500 \text{ kg/cm}^2$; (c) pressure removed; (d) pressure $P \sim 1500 \text{ kg/cm}^2$ reapplied; (e) reapplied pressure removed.

As is seen from Fig. 1, the application of pressure causes a significant decrease of the amplitude and increases the period of the oscillations; the amplitude decreases most in the region of high θ , while the period changes most at small values of θ .

When the pressure is removed, the initial curve is re-established with some amplitude hysteresis. Repetition of the application and removal of pressure reproduces the first cycle, except that the amplitude hysteresis is much less after the second application of pressure.

Figure 2 verifies the data obtained from the rotation diagrams. The period is increased both for $\theta = 80^\circ$ and for $\theta = 20^\circ$, with the increase being 52% in the latter case and 43% in the former. The amplitude decreases in both cases, the decrease being greater for 80° . At this value of θ the amplitude hysteresis is also larger, being about 60%, while at 20° it is only 6-8%. Removal of the pressure leads to complete re-establishment of the periodicity within the limits of experimental error. The slant of the median line in the $\chi(1/H)$ curves, together with the noncoincidence of the zeroes in the rotation diagrams, is explained by a torque component due to the weak magnet anisotropy of the cylinder.

The pressure effect in zinc is thus found to be quite large. It has the following interesting property. Although pressure makes the zinc lattice more isotropic, causing it to approach dense hexagonal packing, the anisotropy of the angular dependence of the periods (or the anisotropy of the Fermi electron surface, which causes this effect) increases.

The influence of pressure on the magnetic properties of Bi at low temperatures has already been communicated.² It is of interest to perform a more detailed investigation of this effect on zinc, a metal whose magnetic properties at low temperatures have been investigated in detail by several authors.³⁻⁵

Monocrystals of Zn were prepared in glass by the Obreimov-Shubnikov method, using "Hilger spectroscopic" metal. The method for creating a pressure of about 1500 kg/cm^2 and measuring the differences in the principal specific susceptibilities of a monocrystal were the same as those used previously.^{2,6} The crystal was oriented in the field so that the suspension axis was perpendicular to the binary crystal axis. The principal axis of the crystal makes an angle θ with the magnetic field vector H in the horizontal plane. The curves shown in Fig. 1 were then obtained for the angular dependence of the torque L_x acting on the crystal at $T = 4.2^\circ \text{ K}$ and $H = 8400$ oersteds, and those of Fig. 2 were obtained for the function $\chi(1/H)$ at two values of θ (20° and 80°).