

The Synthesis, Structure, and Superconducting Properties of New High-Pressure Forms of Tin Phosphide

By P. C. DONOHUE

Received June 2, 1969

Reactions of Sn and P in a tetrahedral anvil press at conditions ranging from 15 to 65 kbars and 600 to 1300° gave intimate mixtures of two new forms of SnP: a tetragonal form having cell dimensions $a = 3.831 \pm 0.001 \text{ \AA}$ and $c = 5.963 \pm 0.001 \text{ \AA}$ and a cubic rock salt type having $a = 5.5359 \pm 0.0001 \text{ \AA}$ at 25°. The crystal structure of the tetragonal phase was refined from powder diffraction intensity data and shown to be similar to that of high-pressure GeP and GeAs. The tetragonal form transformed slowly and irreversibly to the cubic form when heated at ambient pressure between 100 and 200°. Meissner effect measurements showed the tetragonal form to be normal to 1.25°K and the cubic form to be superconducting between 2.8 and 4.0°K.

Introduction

In the Sn-P system, only the compounds SnP¹ and Sn₄P₃² are known. Both have hexagonal crystal structures. Osugi, *et al.*,³ reported the formation of sphalerite-type SnP at 1600–1800° and 40–50 kbars. The powder pattern,⁴ however, was the same as that reported herein for NaCl-type SnP.

Experimental Section

All reactions were run in a tetrahedral anvil press of National Bureau of Standards design⁵ using a cylindrical boron nitride crucible approximately 0.6 cm long and 0.125 cm³ in volume, surrounded by a graphite-sleeve resistance heater inserted in a pyrophyllite tetrahedron. The temperature was measured using a Pt-Rh thermocouple uncorrected for pressure effects and placed at the center of the surface of the cylinder. The temperature at the ends is approximately 30% lower. The operating procedure has been explained elsewhere.⁶

High-purity Sn filings were obtained from a metal rod and passed through a magnet to remove impurity from the file. These were mixed with powdered P and pelleted. Several reactions were run at various conditions. In general, the reactants were cold pressured, then brought to temperature, held for 1 or 2 hr, cooled for about 2 hr, and quenched to room temperature in less than 1 min while pressure was maintained.

All products were characterized by Debye-Scherrer X-ray powder diffraction at 25°. Films were read on a David Mann film reader, Model No. 1222. Unit cell dimensions were refined by a least-squares method with the Nelson-Riley function as one parameter.

Electrical resistivities were measured by a four-probe technique described previously.⁷ Superconducting transition temperatures were measured by observing the Meissner effect at temperatures above 1.25°K.

Results

Filings of Sn were mixed with powdered P in the Sn:P atomic ratio of 1: (0.9–1.1) and treated at the conditions of 800° and 65 kbars, holding 1 hr, cooling 3 hr to 500°,

and quenching. Reactions were also run at 1200° and 65 kbars and at 900° and 15 kbars. The products of all reactions showed similar Debye-Scherrer patterns. Two phases were present, a major tetragonal phase and a minor cubic phase. The Debye-Scherrer pattern of the major phase (Table I) was indexed on the basis of a tetragonal cell: $a = 3.831 \pm 0.001 \text{ \AA}$, $c = 5.963 \pm 0.001 \text{ \AA}$. The weaker lines were indexed on the basis of a cubic cell: $a = 5.5359 \pm 0.0001 \text{ \AA}$. The reflections of the cubic cell were analogous to those of SnAs⁸ but shifted to indicate a smaller cell.

The mixture of tetragonal and cubic phases, when heated in air at ambient pressure, transformed slowly and irreversibly to the cubic phase between 100 and 200°. A broad, shallow endotherm was seen in the dta of several samples. On a few samples the transition could not be seen in the dta.

Resistivity measurements on a polycrystalline piece of SnP which was composed predominantly of the tetragonal form showed metallic behavior: $\rho_{25^\circ\text{C}} = 2 \times 10^{-5} \text{ ohm cm}$, $\rho_{4.2^\circ\text{K}} = 3 \times 10^{-6} \text{ ohm cm}$. Meissner effect was measured on both the tetragonal and cubic forms. The tetragonal form did not show a superconducting transition to 1.25°K; the cubic form showed a superconducting transition temperature between 2.8 and 4.8°K.

Experiments under similar conditions but starting with an Sn:P ratio of 1:2 generally yielded the same mixture of tetragonal and cubic SnP and black P.

Crystal Structure Analysis

The crystal structure of the tetragonal phase was refined from powder intensity data. The structure is similar to that of high-pressure GeP and GeAs.⁹ Intensity data were gathered from a diffractometer tracing by obtaining relative weights of the peaks. A Norelco diffractometer using Cu K α radiation and a LiF bent crystal monochromator was used. A scanning rate of 0.25°/min was used with the chart scaled to 1 in./deg. A smooth background curve was drawn and the peaks were traced onto Cronaflex drafting film,

(1) G. Katz, J. Kohn, and J. Broder, *Acta Cryst.*, **10**, 607 (1957).

(2) O. Olafsson, *Acta Chem. Scand.*, **21**, 1659 (1967).

(3) J. Osugi, R. Namikawa, and Y. Tanaka, *Nippon Kagaku Zasshi*, **87**, 1169 (1966).

(4) J. Osugi, R. Namikawa, and Y. Tanaka, *Rev. Phys. Chem. Japan*, **37** (2), 81 (1967).

(5) E. C. Lloyd, U. O. Hutton, and D. P. Johnson, *J. Res. Natl. Bur. Std.*, **C63**, 59 (1963).

(6) T. A. Bither, C. T. Prewitt, J. L. Gillson, P. E. Bierstedt, R. B. Flippen, and H. S. Young, *Inorg. Chem.*, **5**, 1296 (1966).

(7) T. A. Bither, J. L. Gillson, and H. S. Young, *ibid.*, **5**, 1559 (1966).

(8) ASTM X-Ray Powder Diffraction File Card 15-814.

(9) P. C. Donohue and H. S. Young, submitted for publication.

AUG 26 1970

TABLE I

X-RAY POWDER DIFFRACTION PATTERN OF TETRAGONAL SnP ($a = 3.831 \pm 0.001 \text{ \AA}$, $c = 5.963 \pm 0.001 \text{ \AA}$)

$1/I_0^*$	h	k	l	d (obs.)	d (calc.)
90	1	0	1	3.2189	3.2226
100	0	0	2	2.9784	2.9810
90	1	1	0	2.7105	2.7084
90	1	1	2	2.0030	2.0046
80	2	0	0	1.9151	1.9152
70	1	0	3	1.7625	1.7640
80	2	1	1	1.6458	1.6464
70	2	0	2	1.6103	1.6113
20	0	0	4	1.4901	1.4905
30	2	2	0	1.3545	1.3542
30	1	1	4	1.3068	1.3056
30	2	1	3	1.2972	1.2975
10	3	0	1	1.2473	1.2485
30	2	2	2	1.2332	1.2310
40	3	1	0	1.2111	1.2113
20	2	0	4	1.1756	1.1762
10	1	0	5	1.1381	1.1385
40	3	1	2	1.1224	1.1221
10	3	0	3	1.0744	1.0742
10	3	2	1	1.0462	1.0459
10	2	2	4	1.0018	1.0023
20	2	1	5	.9784	.9786
10	4	0	0	.9577	.9576
10	3	1	4	.9408	.9400
10	3	2	3	.9376	.9369
5	4	1	1	.9156	.9179
10	4	0	2	.9123	.9117
10	3	3	0	.9026	.9028
2	2	0	6	.8816	.8820
5	3	0	5	.8715	.8714
10	3	3	2	.8645	.8640
10	4	2	0	.8569	.8565
10	4	1	3	.8422	.8416
10	1	0	7	.8316	.8314
10	4	2	2	.8231	.8232
5	3	2	5	.7930	.7932

*Head using the David Mann Film Reader.

TABLE II

 I_0 AND I_c FOR TETRAGONAL SnP

h	k	l	I_0	I_c
1	0	1		47.36
-1	0	-1		44.06
			100.00	91.43
0	0	2		20.93
0	0	-2		22.13
			36.95	43.07
1	1	0	72.23	74.84
1	1	2		25.67
-1	-1	-2		27.16
			55.41	52.83
2	0	0	26.59	25.77
1	0	3		13.19
-1	0	-3		11.95
			21.70	25.14
2	1	1		14.25
-2	-1	-1		13.36
			25.70	27.61
2	0	2		12.41
-2	0	-2		13.16
			27.71	25.57
0	0	4		1.68
0	0	-4		1.86
			3.99	3.54
2	2	0	7.60	7.76
1	3	0	12.79	10.45
1	2	3		9.32
-1	-2	-3		8.41
1	1	4		4.26
-1	-1	-4		4.72
			25.60	26.71
3	0	1		2.90
-3	0	-1		2.72
			6.50	5.61
2	0	4		3.01
-2	0	-4		3.34
			6.10	6.35

No. ID4, cut out, and weighed. Fourteen pieces of data were collected.

Least-squares refinement based on the function $\sum w(I_0 - I_c)^2$ was done using a program written by

TABLE III

FINAL PARAMETERS AND BOND DISTANCES AND ANGLES FOR TETRAGONAL SnP

Atom	Position (x, y, z)	Temp factor, \AA^2
Sn	0, 0, 0	0.9 ± 0.3
P	$0, 0, 0.428 \pm 0.010$	2.6 ± 1.6

Atoms ^a	Dist, \AA	Atoms	Angles, deg
Sn(1)-P(2)	2.55 ± 0.06	P(3)-Sn(1)-P(2)	99.0 ± 1.2
Sn(1)-P(3)	2.74 ± 0.01	P(3)-Sn(1)-P(4)	81.0 ± 1.2
Sn(1)-P(4)	3.41 ± 0.06	P(5)-Sn(1)-P(3)	88.6 ± 0.4

^a The numbers on the atoms correspond to the numbers of the atoms in Figure 1.

Prewitt¹⁰ which handles the sums of nonequivalent overlapping reflections. Atomic scattering factors¹¹ corrected for the real and imaginary parts of the anomalous dispersion were used. The imaginary component was applied separately to reflections hkl and $\bar{h}\bar{k}l$. Occupancy factors were held at 2 and the weighting scheme $w = 1/\sigma^2$, with $\sigma = \sqrt{I_0} + 2.0$, was used. The positions 0, 0, z of space group $I4mm$ were used in the refinement with z held at 0.0 for Sn and $z = 0.4$ initially assumed for P.

One scale factor, the single position parameter for P, and two isotropic temperature factors were varied. The R factor defined as $R = \sum |I_0 - I_c| / \sum I_0$ was reduced to 7.8%. The intensity data and final position parameters are shown in Table II. Bond distances were calculated¹² (Table III). The numbers of the atoms correspond to those in Figure 1.

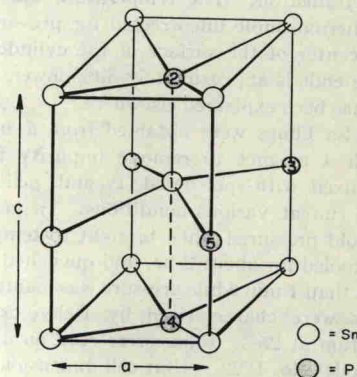


Figure 1.—Structure of SnP.

The cubic structure was shown to be NaCl type. Intensities were read from a Debye-Scherrer pattern using the David Mann film reader. These were compared to the Debye-Scherrer patterns calculated for SnP having the NaCl-type and ZnS-type structures by a program written by Jeitschko and Parthé.¹³ The results (Table IV) clearly indicate the NaCl-type structure to be correct. The pattern is similar to that reported by Osugi, *et al.*,⁴ to be sphalerite type.

(10) C. T. Prewitt, local unpublished computer program.

(11) "International Tables for X-Ray Crystallography," Vol. III, The Kynoch Press, Birmingham, England, 1962, pp 202 and 213, Tables 3.3.1A and 3.3.2A.

(12) L. W. Finger, "University of Minnesota Program for Computing Bond Angles and Distances with Error and Analysis," UMBADTEA, 1965.

(13) W. K. Jeitschko and E. Parthé, unpublished computer program for calculation of X-ray powder diffraction patterns.