

phys. stat. sol. (a) **32**, 301 (1975)

Subject classification: 18.2 and 18.4; 18.1; 21.1; 21.1.1

Institute of Solid State Physics, Academy of Sciences of the USSR, Chernogolovka

Some Peculiarities of the T - P - C Diagram of the System $\text{Fe}_{65}(\text{Ni}_{1-x}\text{Mn}_x)_{35}$

By

G. T. DUBOVKA, E. G. PONYATOVSKII, I. YA. GEORGIEVA, and V. E. ANTONOV

The form of the T - P - C diagram of the $\text{Fe}_{65}(\text{Ni}_{1-x}\text{Mn}_x)_{35}$ system is specified. The alloy with $x = 0.171$ is found to deviate from the linear Curie point dependence on pressure. The interrelation between the magnetic T - C diagram peculiarities and the anomalies of the thermal expansion coefficient and the isotherm of the magnetic susceptibility in the paramagnetic range is investigated.

Уточнен вид фазовой T - P - C диаграммы системы $\text{Fe}_{65}(\text{Ni}_{1-x}\text{Mn}_x)_{35}$. У сплава с $x = 0.171$ обнаружено отклонение зависимости точки Кюри от давления от линейной. Исследована взаимосвязь между особенностями магнитной T - C диаграммы и аномалиями к.л.р. и изотермы магнитной восприимчивости в парамагнитной области.

1. Introduction

One of the reasons which recently caused an increasing interest in investigations of ternary alloys on Fe-Ni invar base is the possibility to study anomalies of physical properties by varying the ratio of alloying elements. These anomalies always appear simultaneously in binary invars: low magnitude of the Curie points T_C and spontaneous magnetization at 0 °K, anomalies of P - V - T relations (including thermal expansion), decreasing stability of the γ -phase to $\gamma \rightarrow \alpha$ transformation, etc.

The Fe-Ni-Mn system gives the opportunity to study the transition from alloys being ferromagnetically ordered at low temperature (Ni-rich alloys) to those being ordered antiferromagnetically (Mn-rich alloys) [1].

In the present work the T - P - C phase diagram of the Fe-Ni-Mn system was specified for $\text{Fe}_{65}(\text{Ni}_{1-x}\text{Mn}_x)_{35}$, the relation of the peculiarities of the diagram with anomalies of linear expansion and magnetic susceptibility in the paramagnetic region was investigated.

2. Experimental

The alloys were prepared from electrolytic Ni, Mn, and Fe carbonyl by melting in argon atmosphere in an induction furnace. The melts were subjected to homogeneous annealing at 1100 °C for 6 h and subsequent quenching in water. The susceptibility χ was measured by the Faraday-Sucksmith method with an accuracy of 0.1×10^{-4} e.m.u./g. Alloys No. 1, 2, 3, 8, 9 (Table 1) were investigated at hydrostatic pressures up to 20 kbar. The pressure was measured by a manganin wire gauge with an accuracy of ± 100 bar, the temperature by a chromel-alumel thermocouple with an accuracy of ± 1 deg. Alloys No. 4 and 5 were investigated using AgCl as the pressure transmitting medium. In these

Table 1

No.	content (wt%)		x	T_C (°K)	T_N (°K)	$-dT_{C,N}/dP$ (deg kbar ⁻¹)
	Mn	Ni				
1	0	35	0.000	467		4.4 ± 0.1
2	1.5	33.5	0.043	402		5.0 ± 0.1
3	3.0	32	0.086	353		4.8 ± 0.15
4	4.5	30.5	0.129	228		4.2 ± 0.4
5	6	29	0.171	190		3.7 ± 0.3
6	8	27	0.229	90		—
7	24	11	0.686		253	—
8	29	6	0.829		341	0.6 ± 0.2
9	35	0	1.000		442	0.9 ± 0.1

cases the pressure up to 25 kbar was measured with an accuracy of ± 1 kbar. The Curie points T_C were determined by the differential transformer method [2] using the temperature dependence of the initial magnetic permeability with an accuracy of ± 3 deg. The Néel points T_N were determined by controlling the position of the bend of the temperature dependence curve of electrical resistance with an accuracy of ± 5 deg. The fact that these bends in alloys No. 8 and 9 correspond to the Néel points was proved by means of neutron diffraction investigation.

3. Results and Discussion

All the investigated alloys had a disordered f.c.c. structure. The obtained magnitudes of T_C , T_N and initial values of dT_C/dP and dT_N/dP are given in Table 1 and Fig. 1. The T - C diagram at atmospheric pressure is in good agreement with data given in [1, 3]. The considerable disagreement of the values dT_C/dP obtained in [3] with our data might possibly be due to great errors in the measurements [3] resulting from too small maximal pressure (3 to 5 kbar) used in the work.

For all the alloys studied under pressure except the alloy No. 5, T_C and T_N decrease linearly with increasing pressure. In the alloy No. 5, however, the marked divergence of the $T_C(P)$ dependence from the linear one is noticed (Fig. 2). It is worth pointing out that from all the alloys studied under pressure

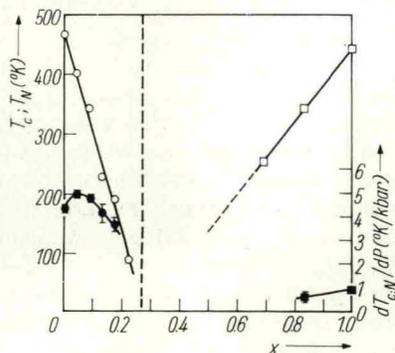


Fig. 1. The phase diagram of magnetic transitions in the $Fe_{65}(Ni_{1-x}Mn_x)_{35}$ system at atmospheric pressure and dependences of dT_C/dP and dT_N/dP on composition. \circ T_C ; \bullet dT_C/dP ; \square T_N ; \blacksquare dT_N/dP