

Fig. 2. The  $T_C(P)$  and  $T_C^2(P)$  dependences for alloy No. 5 ( $x = 0.171$ )

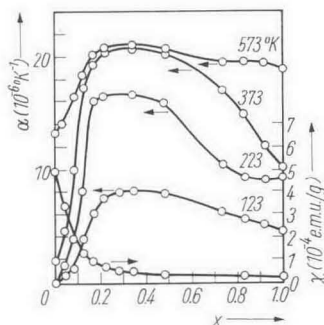


Fig. 3. The dependences of the linear expansion coefficient  $\alpha$  and magnetic susceptibility  $\chi$  at 573 °K on alloy composition

this specimen had the lowest  $T_C$  and that for the alloy with similar composition (No. 4) investigated under the same (quasi-hydrostatic) conditions the  $T_C(P)$  dependence deviates from the linear one only slightly and lies within the experimental error.

It is seen in Fig. 2 that the  $P(T_C)$  dependence for the alloy No. 5 is nearly parabolic in the investigated temperature range. The very dependence

$$\frac{dT_C}{dP} = -\frac{A}{T_C},$$

where  $A$  is the constant given by Wohlfarth's approximation [4] of a very weak itinerant ferromagnetism (in our case  $A \approx 700 \text{ deg}^2 \text{ kbar}^{-1}$ ). The fact that such an approximation may be used to describe the temperature dependence of magnetization of the system  $\text{Fe}_{65}(\text{Ni}_{1-x}\text{Mn}_x)_{35}$  for  $0.15 < x < 0.3$  was already illustrated in [5].

The results of measurements of the linear expansion coefficient  $\alpha$  at different temperatures and the isotherm of magnetic susceptibility  $\chi$  at 573 °K (in the paramagnetic range) are given in Fig. 3. It follows from Fig. 3 that on substituting Ni by manganese  $\alpha$  increases sharply near the composition  $\text{Fe}_{65}\text{Ni}_{35}$  and decreases more smoothly near  $\text{Fe}_{65}\text{Mn}_{35}$  at all temperatures. For  $\chi$  one can observe a sharp drop in the  $0 < x < 0.3$  range and a weak dependence on concentration at higher Mn contents. Thus it is seen from Fig. 3 that both the functional dependences  $\alpha(x)$  and  $\chi(x)$  are different in the regions  $x \lesssim 0.3$  and  $x \gtrsim 0.3$  up to temperatures which are considerable higher than those of magnetic ordering of the investigated samples (the boundary between these regions is conventionally shown in Fig. 1 by a dashed line). All the investigated alloys had the same f.c.c. lattice at all temperatures, so the difference in the behaviour of the  $\alpha(x)$  and  $\chi(x)$  dependences in the mentioned regions may be due to the difference in the electron configuration in the paramagnetic state of the samples which are ferromagnetics ( $x \lesssim 0.3$ ) and antiferromagnetics ( $x \gtrsim 0.3$ ) at low temperatures.

It is seen from Fig. 1 that a region of alloys paramagnetic down to temperatures close to 0 °K, may appear or extend with increasing pressure. Thus, for example, extrapolation gives  $T_C = 0$  °K at  $P < 30$  kbar (Fig. 2) for the alloy

No. 5. Similar speculations are true for Fe-Ni-Mn antiferromagnetic alloys as well. The number of the  $s + d$  external electrons is considered as a criterion of a magnetic ordering to exist in alloys on the basis of d-metals in some papers [6, 7]. High pressure does not change this number in our Fe-Ni-Mn alloys, but may transform, for example, the state of alloy No. 5 from ferromagnetic at temperatures below 190 °K to paramagnetic at temperatures close to 0 °K. This fact seems to be unfavourable for the use of the number of external electrons as a criterion of magnetic ordering in alloys of d-metals.

#### Acknowledgements

The authors thank R. Y. Sizov for the Néel point determination by means of neutron diffraction and E. I. Potapov for his help in carrying out the experiments.

#### References

- [1] M. SHIGA, J. Phys. Soc. Japan **22**, 539 (1967).
- [2] G. T. DUBOVKA and E. G. PONYATOVSKII, Fiz. Metallov i Metallovedenie **33**, 640 (1972).
- [3] J. NAKAMURA, M. HAYASE, M. SHIGA, Y. MIYAMOTO, and N. KAWAI, J. Phys. Soc. Japan **30**, 720 (1971).
- [4] E. P. WOHLFARTH, Phys. Letters A **28**, 569 (1969).
- [5] B. K. PONOMARYOV and S. V. ALEKSANDROVICH, Zh. eksper. teor. Fiz. **67**, 1965 (1974).
- [6] S. CHIKAMUZI, T. MIZOGUCHI, and N. YAMAGUCHI, J. appl. Phys. **39**, 935 (1968).
- [7] V. M. KALININ, Fiz. Metallov i Metallovedenie **39**, 439 (1975).

(Received September 3, 1975)