

volume change is constant at fixed p and T , the isotherm of the second phase (ϵ - phase) can be easily found by shifting the first phase by the amount of the volume change ($v_2 - v_1$).

TABLE VI
Physical Data for α - iron

Parameter	Values	Dimension	Reference
v_o (initial volume)	.1275	cc/g	(33)
α_1 (thermal expansion coefficient)	36.3×10^{-6}	$1/K^o (\text{degK})^{-1}$	(33)
c_{v1} (heat capacity)	$.4447 \times 10^{-5}$	Mbcc/g o K	(33)
p_M (transition pressure)	.130	Mb	(10)
$(dp/dT)_m$ (equilibrium)	-.000065	Mb/K o	(10)
Δv (volume difference)	-.004	cc/g	(10)
a_1	1.667	Mb	(32)
a_2	3.4	Mb	(32)
a_3	0	Mb	(32)
Γ	1.6	. . .	(34)
$c_{v,m}$	$.46 \times 10^{-5}$	Mbcc/g o K	*
T_o	300 o K	o K	

*See Appendix III.

Once the equation of state is known, the expression for α_{α}^{eq} can be easily found from Eq. (4.4), which includes the room temperature approximation for $v_1(T)$. Suppose we specify the room temperature transformation by the isotherm AB in Fig. 4.1;

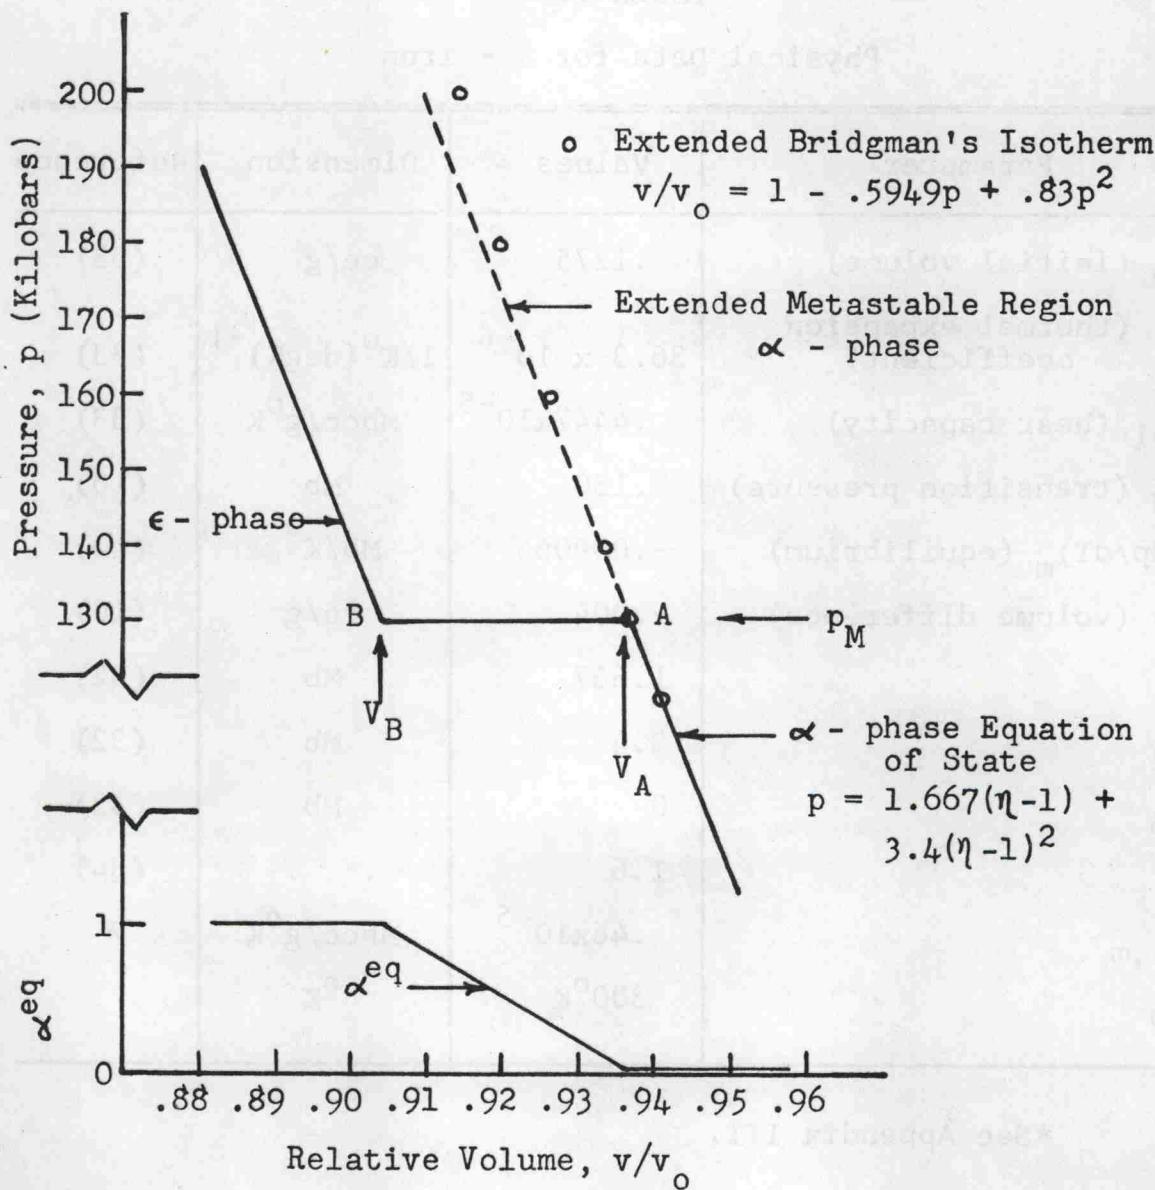


Fig. 4.1--Temperature Independent Equation of State of Iron and α^{eq}