

in order to illustrate the fits of the various parameters, the curves corresponding to the $\langle 111 \rangle$ orientation are omitted.

5.1. Resistivity curve

The fits to the resistivity curves were made by fixing the experimental point at 30 kbar and varying ΔE_0 and S' for a particular value of S . It can be seen from figures 3 and 4 that the height and shape of the maximum depends sensitively on S , and shows that a reasonable value would lie between 3 and 5 (ie 4 ± 1). This is in excellent agreement with Jayaraman and Kosicki (1968). The value of S' corresponding to this value of S can be seen to

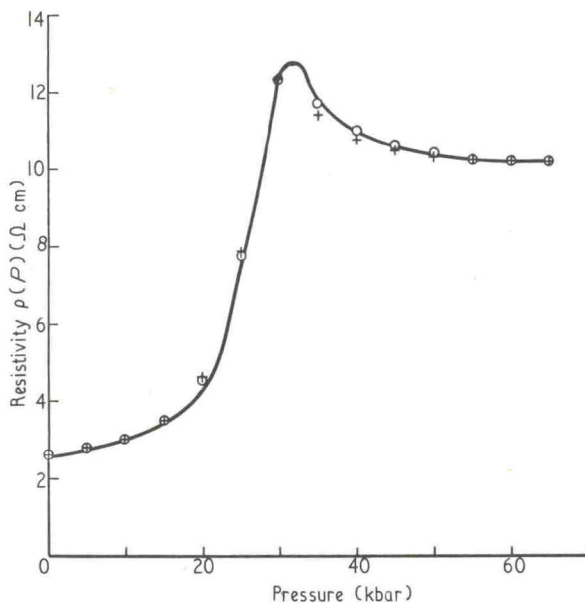


Figure 4. Theoretical fits of high pressure resistivity data in n type Ge for $N_0 = 5.5$, $\Delta E_0 = 0.186$ eV, and values of S from 3 to 5. Full curve, experimental; \circ $S = 3$, $S' = 0.188$; $+$ $S = 5$, $S' = 0.099$.

be near 0.1 to 0.2, provided N_0 is greater than 2.7. Jayaraman and Kosicki (1968) obtained S' between 0.1 and 0.36 for $N_0 \sim 2.7$. We further find that any increase in N_0 must be accompanied by an increase in ΔE_0 to obtain the best resistivity fit, and for $N_0 = 5.5$ we have ΔE_0 is 0.186 ± 0.01 eV.

The resistivity theoretical fits have the same deviations as found by Fawcett and Paige (1971) for their determination of the $L_1-\Delta_1$ nonequivalent intervalley scattering coupling constant, that is a steeper rise in resistivity at a lower pressure than observed experimentally, and more pronounced saturation in the very high pressure region.

5.2. Hall mobility curve

These were obtained from R_H/ρ (figures 5 and 6) and proved to be extremely sensitive to the chosen value of S' . It was extremely difficult to obtain a wholly accurate fit taking different values of S and S' in the region just before and at band cross-over. The integrals in this case were solved exactly since the approximate expressions of Nathan *et al.* (1961) produced even worse fits. To obtain reasonable fits for $S = 4$, it is evident that N_0 must be much greater than 2.7 (taking the Cardona and Pollak (1965) Δ_1 effective mass). Figure 5 illustrates how the mobility is particularly sensitive to S' near band cross-over, in the 25–35 kbar range. Figure 6 shows also how an increase in N_0 lowers the points near 25 kbar and

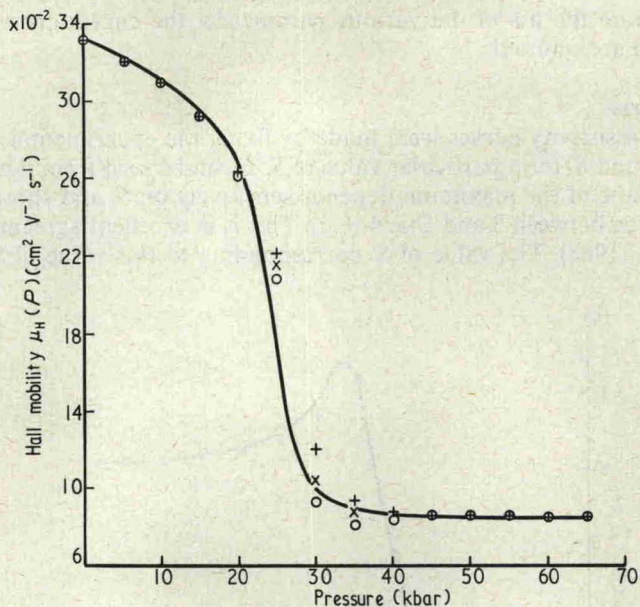


Figure 5. Theoretical fits of high pressure mobility data in n type Ge for $N_0 = 5.5$, $S = 5$, and $\Delta E_0 = 0.186$ eV for: + $S' = 0$; \times $S' = 0.1$; \circ $S' = 0.2$. Note that the largest changes occur near band cross-over in the 25–35 kbar range. Full curve, experimental.

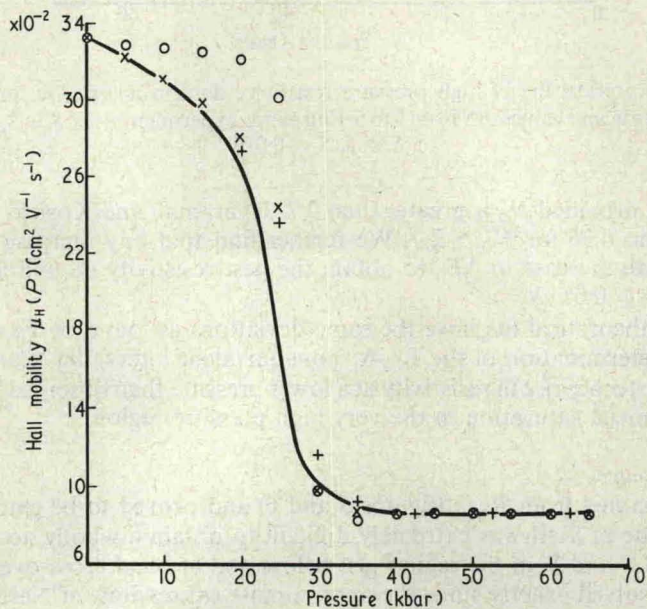


Figure 6. Theoretical fits of high pressure mobility data in n type Ge for constant $S (=4)$ and $S' (=0)$, which illustrates that a high value of N_0 is required ($N_0 = 1.55$ is obviously too low). Full curve, experimental; \circ $N_0 = 1.55$, $\Delta E_0 = 0.177$ eV; \times $N_0 = 2.7$, $\Delta E_0 = 0.18$ eV; + $N_0 = 4.2$, $\Delta E_0 = 0.185$ eV.