

The results on the influence of high pressure on the energy gap and critical temperature of tin are represented in Fig. 4.

From experiments the following values are found:

$$\frac{dT_c^{\text{Sn}}}{dP} = -(4.8 \pm 0.3) \times 10^{-5} \frac{\text{K}}{\text{atm}},$$

$$\frac{d2\Delta}{dP} = -(-1.85 \pm 0.1) \times 10^{-5} \frac{\text{meV}}{\text{atm}}.$$

Thus it was shown by means of direct experiment that in the case of tin as for lead $2\Delta/kT_c$ changes with pressure. Analysing the experimental data and the data of (1 to 3) on lead, and estimating the change of Θ_D with pressure (6, 7) it is interesting to mark that the magnitude of the shift of $2\Delta/kT_c$ with pressure coincides with the change of T_c/Θ_D .

Multi-band effects can possibly cause a gap decrease with pressure. This question is studied now experimentally.

In conclusion we should like to point out the following: Observation of the Josephson dc (8) under pressure (Fig. 1) apparently shows the essential role of fluctuations in superconducting tunnelling.

Acknowledgements

We are grateful to I. Ivanchenko and L. Zilberman for helpful discussions of the superconducting tunnelling problem, V. I. Makarov for useful remarks and advices, V. V. Shevtsov for constant technical aid, V. P. Raevskii for some innovations in making high pressure cells.

References

- (1) A. A. GALKIN and V. M. SVISTUNOV, *phys. stat. sol.* **26**, K55 (1968).
- (2) I. P. FRANCK and W. T. KEELER, *Phys. Letters (Netherlands)* **25A**, 624 (1967).
- (3) N. V. ZAVARITSKII, E. S. ITSKEVICH, and A. N. VORONOVSKII, *Zh. eksper. teor. Fiz., Pisma* **7**, 271 (1968).
- (4) B. T. GEILIKMAN and V. KRESIN, *Fiz. tverd. Tela* **7**, 3297 (1965).
- (5) I. BARDEEN, L. COOPER, and I. SCHRIEFFER, *Phys. Rev.* **108**, 1175 (1957).

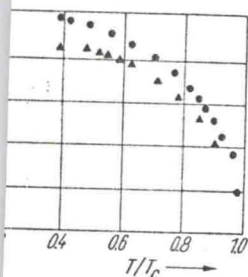


Fig. 2

at $P = 0$ and $P = 8.2$ katm.

of tin at a pressure of 8.2 katm;

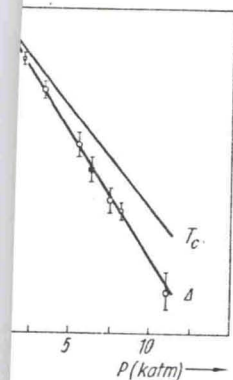


Fig. 4

pressures. Normalized units are

gap and critical temperature of
 $dT_c/dP = -4.8 \times 10^{-5} \text{ K/atm};$