

Some Proposals for Transformation Mechanisms of the Li_2ZrF_6 , Trirutile and Na_2SiF_6 Structure Types: Simple Cation Rearrangements

JEAN GALY AND STEN ANDERSSON

Service de Chimie Minérale Structurale de la Faculté des Sciences de Bordeaux associée au CNRS, 33-Talence, France

and

Chemical Centre, Department of Inorganic Chemistry 2, Box 740, S-220 07 Lund 7, Sweden.

Received March 8, 1971

Under high pressure, rutile transforms into a structure of the $\alpha\text{-PbO}_2$ type. In a previous paper (1) we proposed a simple mechanism for this transformation which is illustrated in Fig. 1. We now suggest similar cation displacements to interconvert the Li_2ZrF_6 , trirutile, Na_2SiF_6 and columbite structure types.

When Li_2NbOF_5 was reported (2) as being isostructural with Li_2ZrF_6 (3), a picture was made showing its relation to the rutile structure. In Figs. 2a and b, the structures of trirutile and Li_2NbOF_5 are compared; Fig. 3 shows how the Li_2ZrF_6 structure type can transform into the trirutile type if 50% of the cations are shifted in the way

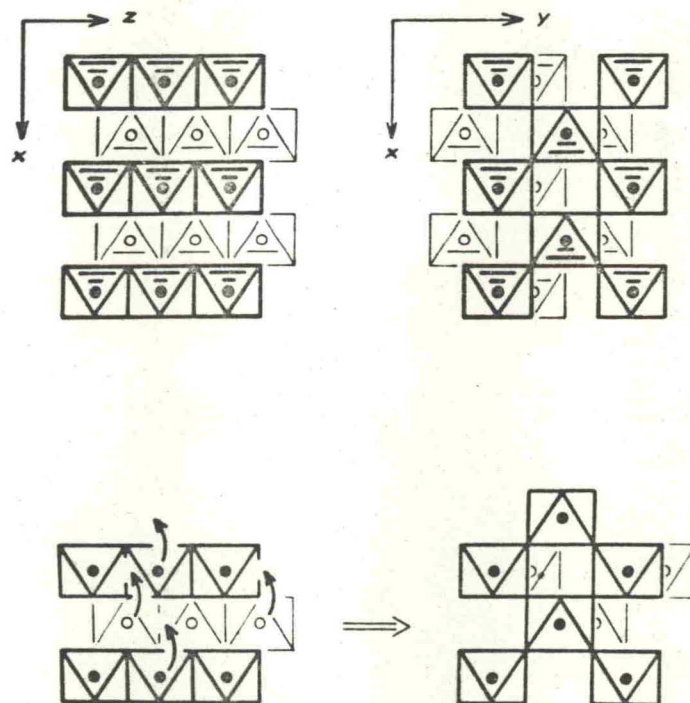


FIG. 1. The rutile structure (upper left) is compared with the $\alpha\text{-PbO}_2$ structure type (upper right). Below is shown a possible mechanism for the rutile \rightarrow $\alpha\text{-PbO}_2$ transformation. Cation movements are indicated with arrows.

Ga^{3+} ions. Finally crystal structure of still undetermined before we can discuss

anishi of Broadcasting an Broadcasting Co. material. We thank Dr. formation of a Russian moto for his warm

ND V. S. STUBICAN, J.

233, 1279 (1951).
ures", 2nd. ed. Vol. 3,
965.

VEISS, Z. *Naturforsch.*

m. 2, 6 (1970).

VEISS, Z. *Naturforsch.*

n.

anet. *Interiors* 3, 109

A. SEMILETOV, T. V.
HITAR, *Kristallografiya*

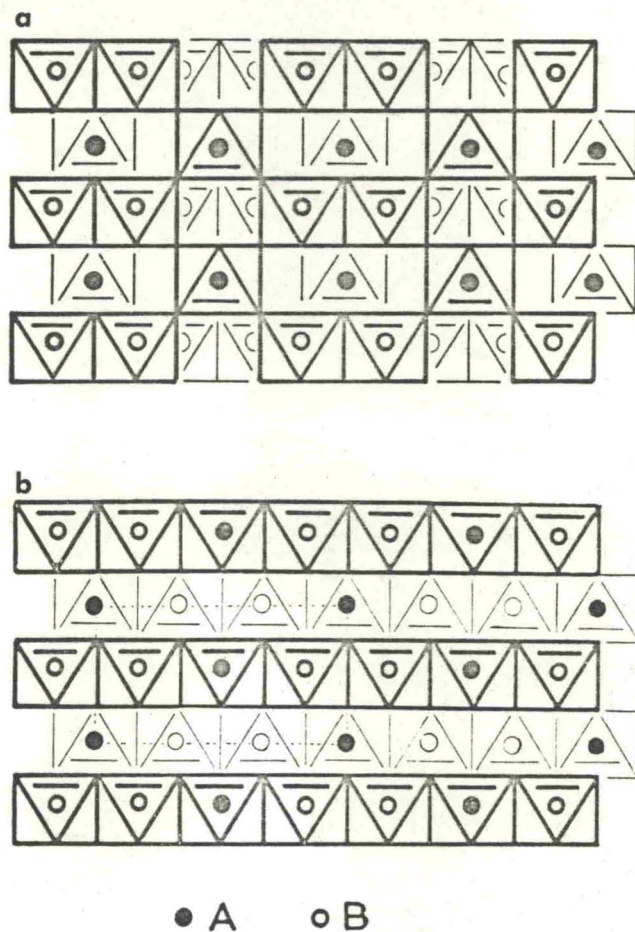


FIG. 2. In (a) the Li_2ZrF_6 structure type (Li_2NbOF_5) is given. In (b) the trirutile structure of the composition AB_2X_6 . In both the structures, A corresponds to filled circles, and open circles are the B-atoms.

indicated by the curved arrows, and without disorder. To our knowledge, no such transformation has been reported for the compounds Li_2NbOF_5 and Li_2ZrF_6 . However, $\alpha\text{-Li}_2\text{SnF}_6$ of the Li_2ZrF_6 type has been found to transform to a structure of the trirutile type, designated $\beta\text{-Li}_2\text{SnF}_6$ at 510°C (4).

Another interesting transformation was reported recently (5, 6). At about 400°C , $\alpha\text{-Li}_2\text{GeF}_6$, of the trirutile type, transforms to $\beta\text{-Li}_2\text{GeF}_6$ which has the Na_2SiF_6 type structure (7). Figure 4 shows the Na_2SiF_6 structure projected along the c -axis, and Fig. 5 the trirutile structure in an analogous projection. The geometrical relation between these structures can be shown by considering the Na_2SiF_6 type. The cations in the octahedra drawn with heavy lines are at $z = \frac{1}{2}$, those in the lighter octahedra at $z = 0$. If the metal atoms at $z = 0$ in m -planes move

to $z = \frac{1}{2}$, and those at $z = \frac{1}{2}$ in n -planes to $z = 0$, the trirutile structure is obtained. This involves half the cations passing through octahedral faces along half the c -axis; the anion lattice remains intact. If the A and B atoms keep their relative order during the transformation, the ordered Na_2SiF_6 structure type may, in the reverse way, be geometrically derived directly from the ordered trirutile type. That $\beta\text{-Li}_2\text{SnF}_6$ and $\beta\text{-Li}_2\text{GeF}_6$ are formed as ordered compounds, with, respectively, the trirutile and Na_2SiF_6 structures, indicates that the geometrical proposals described here may very well be correct mechanisms.

All these compounds have approximately the same (hexagonally close packed) anion arrangement. At very high pressures the preferred cation arrangement seems to be like that in the $\alpha\text{-PbO}$

FIG. 2
type.

structu
genera
(order
analog

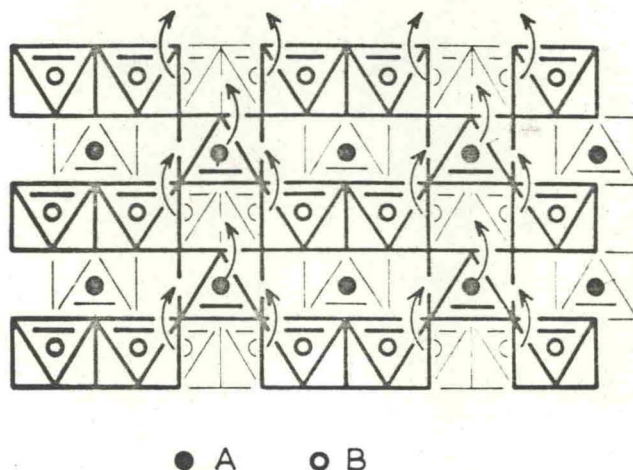


FIG. 3. If cations are shifted in the way described by arrows, the trirutile structure is formed from the Li_2ZrF_6 structure type.

structure type. Amongst the ternary compounds of general formula AB_2X_6 a similar arrangement of (ordered) cations occurs in columbite FeNb_2O_6 . By analogy with the rutile $\rightleftharpoons \alpha\text{-PbO}_2$ transformation,

we might therefore expect the AB_2X_6 compounds discussed above to transform at high enough pressures to a ternary analog of $\alpha\text{-PbO}_2$, possibly with the cations ordered as in FeNb_2O_6 .

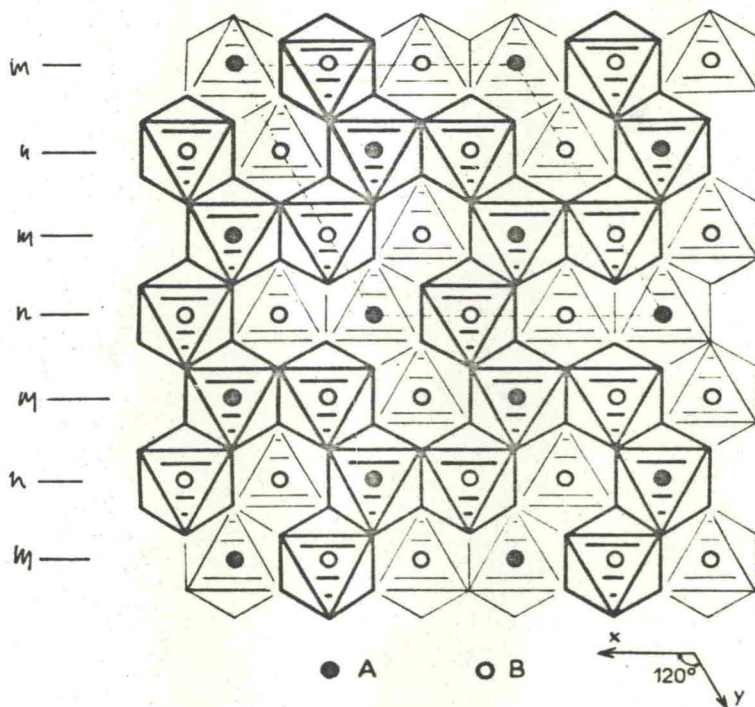


FIG. 4. The Na_2SiF_6 structure type.

osition AB_2X_6 . In both

n -planes to $z=0$. ned. This involves h octahedral faces on lattice remains their relative order ordered Na_2SiF_6 . erse way, be geo- n the ordered tri- and $\beta\text{-Li}_2\text{GeF}_6$ are with, respectively. res, indicates that bed here may very

approximately the d) anion arrange- ie preferred cation hat in the $\alpha\text{-PbO}_2$:

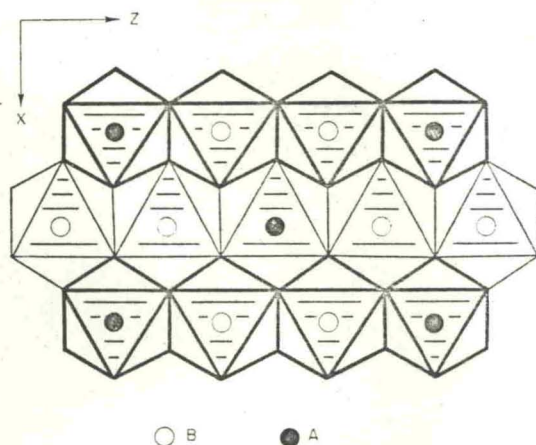


FIG. 5. The trirutile structure type.

It would be interesting to study the effects of applied pressure in the high temperature experiments referred to above.

In the meantime a tentative pressure-temperature phase diagram is given in Fig. 6. Its construction is based on the observations that

- (a) α - LiSnF_6 transforms to β - Li_2SnF_6 ,
- (b) α - Li_2GeF_6 transforms to β - Li_2GeF_6 at high temperatures and
- (c) rutile transforms to a structure of the α - PbO_2 type at high pressure.

Acknowledgment

One of us (S.A.) has a research grant from the Swedish Natural Science Research Council.

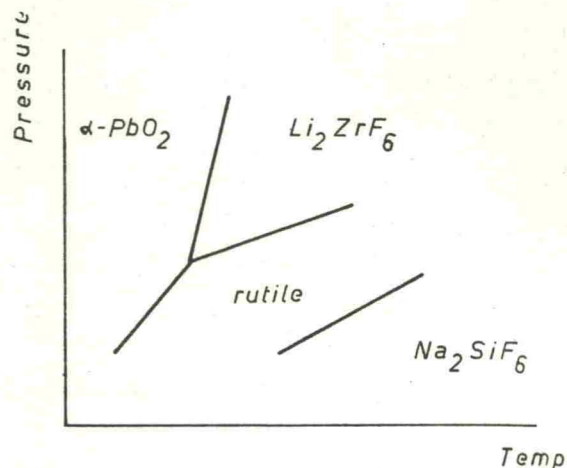


FIG. 6. Tentative temperature-pressure phase diagram for the various MX_2 structure types discussed.

References

1. S. ANDERSSON AND J. GALY, *Bull. Soc. Chim. France*, 1065 (1969).
2. J. GALY, S. ANDERSSON, AND J. PORTIER, *Acta Chem. Scand.* **23**, 2949 (1969).
3. E. HOPPE AND W. DÄHNE, *Naturwiss.* **47**, 397 (1960).
4. C. HEBECKER AND R. HOPPE, *Naturwiss.* **53**, 106 (1966).
5. J. PORTIER, F. MÉNIL, AND J. GRANNEC, *C.R. Acad. Sci.* **269**, 327 (1969).
6. J. PORTIER, F. MENIL, AND P. HAGENMULLER, *Bull. Soc. Chim. France*, 3485 (1970).
7. A. ZALKIN, J. D. FORRESTER, AND D. H. TEMPLETON, *Acta Cryst.* **17**, 1408 (1954).