

SOLUBILITY OF CORUNDUM IN AQUEOUS ALKALINE  
SOLUTIONS AT ELEVATED TEMPERATURES AND PRESSURES

I. G. Ganeev, M. A. Menkovskii,  
and V. N. Rummyantsev

UDC 542.61:548.58

Dependence of the Solubility of Corundum on Pressure. Barns, Laudise, and Shields [1] have shown that the pressure dependence of the solubility of corundum ( $\alpha\text{-Al}_2\text{O}_3$ ) in aqueous solutions of sodium carbonate is complex. For example, at  $430^\circ\text{C}$ , the solubility of corundum in 3.4 m  $\text{Na}_2\text{CO}_3$  increases with an increase in pressure up to 1380 bars, but a further increase in pressure has no effect on the solubility, and even possibly decreases it somewhat. It is also known that the solubility of sodium carbonate in water at elevated temperatures depends greatly on pressure [2]. It might well be assumed that the solubility of corundum in aqueous solutions of sodium carbonate depends directly on the state of the  $\text{Na}_2\text{CO}_3$  in the system.

The results of an experimental confirmation\* of this assumption are shown in Fig. 1.

A comparison of the experimentally determined pressure dependence of the solubility of corundum in aqueous  $\text{Na}_2\text{CO}_3$  at  $460^\circ$  with the pressure dependence of the solubility of  $\text{Na}_2\text{CO}_3$  in water at this same temperature [2] indicates that the increase in corundum solubility with increasing pressure (at constant solution concentration) continues until all of the  $\text{Na}_2\text{CO}_3$  introduced into the system has gone into solution. A further increase in pressure has a very slight effect on the solubility of corundum.

\*The solubility of corundum was studied in 50-ml autoclaves equipped with tightly fitting protective silver inserts by determining the loss in weight following quenching [1, 3]. Synthetic corundum leaves and cp reagents were used in the experiments. According to Kuznetsov [3], solution of corundum under hydrothermal conditions requires 1.5 days for establishment of equilibrium. On this basis, we elected to hold our solutions at the given temperature and pressure for from 2 to 5 days, since this ensured that equilibrium was reached in the system. The pressure under any set of experimental conditions was determined from the P-F-T diagrams published by Samoilovich for aqueous solutions of sodium carbonate and sodium hydroxide [4]. The temperature was held at the desired value within  $\pm 3^\circ$ .

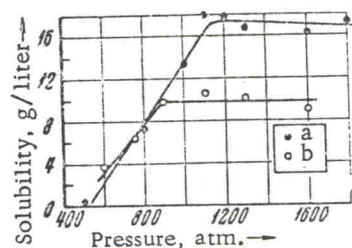


Fig. 1

Fig. 1. Dependence of the solubility of corundum in aqueous sodium carbonate solutions on pressure at  $460^\circ$ .  $\text{Na}_2\text{CO}_3$  concentration: a) 50 g/liter; b) 25 g/liter.

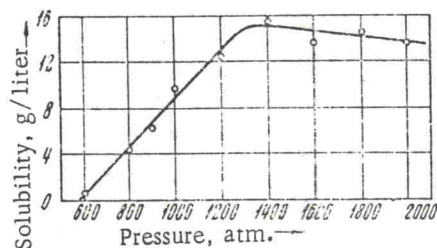


Fig. 2

Fig. 2. Pressure dependence of the solubility of corundum in aqueous  $\text{NaHCO}_3$  with a concentration of 100 g/liter at  $500^\circ$ .

Moscow Institute of Mining. (Presented by Academician N. M. Zhavoronkov, July 16, 1969.) Translated from *Doklady Akademii Nauk SSSR*, Vol. 191, No. 5, pp. 1057-1059, April, 1970. Original article submitted July 16, 1969.

©1970 Consultants Bureau, a division of Plenum Publishing Corporation, 227 West 17th Street, New York, N. Y. 10011. All rights reserved. This article cannot be reproduced for any purpose whatsoever without permission of the publisher. A copy of this article is available from the publisher for \$15.00.