

Reprinted from: LOW TEMPERATURE PHYSICS-LT 13, VOL. 2

Edited by K. D. Timmerhaus, W. J. O'Sullivan, and E. F. Hammel  
Book available from: Plenum Publishing Corporation  
227 West 17th Street, New York, New York 10011

## Kondo Effect in YCe under Pressure

W. Gey and M. Dietrich

*Universität und Kernforschungszentrum Karlsruhe  
Karlsruhe, West Germany*

and

E. Umlauf

*Zentralinstitut für Tieftemperaturforschung  
Garching, Germany*

### Introduction

In an earlier paper we showed that the Kondo temperature  $T_K$  of LaCe increases upon application of pressure.<sup>1</sup> This result was derived from the pressure dependence of the superconducting transition temperature by applying the theory of Müller-Hartmann and Zittartz.<sup>2</sup> It was independently derived from the temperature dependence of the resistance  $R$  at different pressures and the variation of  $R$  with pressure at constant temperature, using the calculation of Hamann.<sup>3</sup>

Similar measurements have been reported by other authors, who instead interpreted their results in terms of a magnetic–nonmagnetic transition of the Ce impurities at pressures at which both the slope  $dR/d(\ln T)$  and the superconducting pair-breaking effect decrease.<sup>4</sup> Particularly, the disappearance of the resistance minimum of YCe under pressure has been presented as an argument for the vanishing magnetic moment of the cerium impurities.<sup>5</sup> This explanation has become widely accepted in the literature; review articles have already appeared.<sup>6,7</sup>

We have reinvestigated the pressure dependence of the resistance anomaly of Y 1 at. % Ce. In analogy with the results for LaCe and also for CuFe,<sup>8</sup> we expected a shift of  $T_K$  to higher temperatures with pressure. The experimental results clearly show that this is so. The Kondo temperature is raised from 17°K at zero pressure to approximately 110°K at 30 kbar, while the magnitude of the anomaly is unchanged.

### Results

Measurements were taken using a piston-cylinder technique in a pair-of-tongs apparatus described earlier.<sup>9</sup> It is sensitive to  $\pm 100$  bar at zero pressure and can be cycled repeatedly up to 45 kbar. Steatite has proved to be a sufficiently hydrostatic medium.<sup>10</sup> Samples of pure yttrium and Y 1 at. % Ce were mounted in series in the pressure cell and fed by the same current.

Figure 1 shows the resistance vs.  $\ln T$  for both Y and YCe as obtained directly in the low-temperature regime. The Y sample shows normal behavior at all pressures

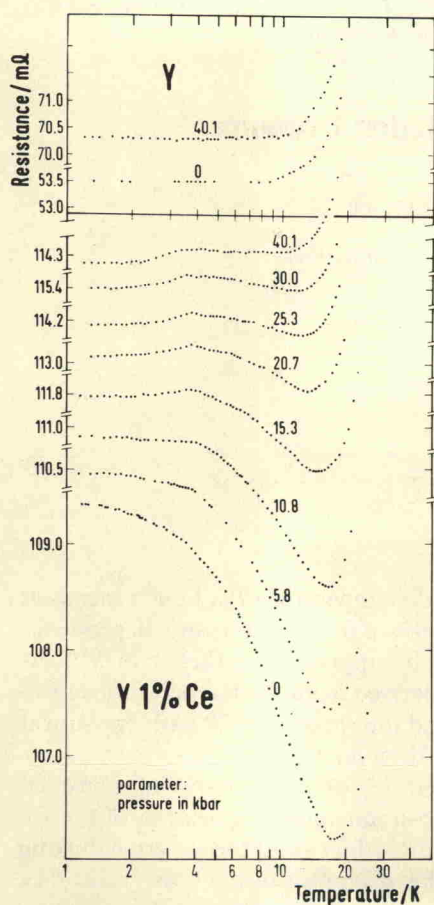


Fig. 1. Low-temperature electrical resistance of Y and Y 1 at. % Ce vs. temperature at various pressures.

up to 40 kbar. At low temperatures the phonon dependence is  $T^{4.0}$  for all pressures. Only data for 0 and 40 kbar are given.

The decrease with pressure of the depth of the resistivity minimum in YCe is qualitatively in accord with the results of Maple and Wittig.<sup>5</sup> It led these authors to conclude that the magnetic moment of the Ce impurity vanishes in this pressure regime. In contrast, our results show that this is due to an increase of the Kondo temperature. In order to see this, it is necessary to isolate the magnetic part of the temperature-dependent resistivity from the phonon part at higher temperatures. This can be achieved as follows: Near room temperature the magnetic part of the resistance is negligibly small, at least at low pressure, i.e., low Kondo temperatures. Thus the slope of a  $R_Y$  vs.  $R_{YCe}$  plot near 300°K determines the geometric factor  $m$  between both samples. This factor does not change by more than 0.8% for all pressures up to 25.3 kbar. Assuming the constancy of the residual resistance up to room temperature (i.e., Matthiessen's rule) and that the  $T$  dependence of the phonon part of the resistance is identical for YCe and Y, one obtains the magnetic resistance anomaly.

Figure 2 shows the result of this procedure. The main physical result is that an