Lattice parameters obtained at these temperatures were excluded from Fig. 1 and from the least squares fits of the data.

The first run with LaRu₂ indicated that at about 300°C the lattice constant changed very little with temperature. In order to check this behavior a second run was made. The data from the second run, however, indicated no abnormal behavior at that temperature. This accounts for the high concentration of points shown near 300°C for LaRu₂ in Fig. 1.

The fits of the lattice constant *versus* temperature data are summarized in Table I. From these constants the instantaneous linear thermal coefficients were calculated by using eqn. (5). The resulting α_t values are shown in Fig. 2 as a function of temperature.

TABLE I SUMMARY OF X-RAY THERMAL EXPANSION DATA

Compound	Temp. range (°C)	No. of points	$a = A + Bt + Ct^2$			Stand. dev.	$\bar{a} \times 10^{-6}$ /°C
			Λ	B × 10 ⁵	C × 108	of fit $\sigma \times 10^4$ (A)	20° to tmax
LaRu ₂	16°-800°	38ª	7.7025	7.021	1.75	±11.01	10.98
CeRu ₂	19°-900°	26h	7.5354	5.700	3.31	7.72	11.59
PrRu ₂	19°-650°	23h	7.6210	6.923	0.711	6.01	9.713

a Data obtained from Unicam cameras 1 and 2 and CRL camera.

^b Data obtained from one of the Unicam cameras and the CRL camera.

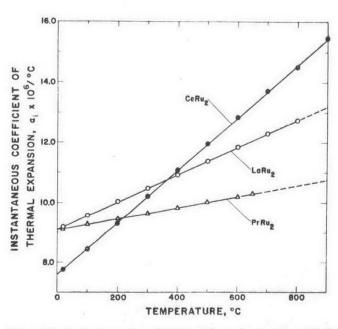


Fig. 2. The instantaneous coefficient of thermal expansion of $LaRu_2$, $CeRu_2$ and $PrRu_2$ as a function of temperature.

J. Less-Common Metals, 8 (1965) 217-221