

Superconductivity of Nb_3Sn

B. T. MATTHIAS, T. H. GEBALLE, S. GELLER, AND E. CORENZWIT
Bell Telephone Laboratories, Murray Hill, New Jersey
(Received June 10, 1954)

Intermetallic compounds of niobium and tantalum with tin have been found. The superconducting transition temperature of Nb_3Sn at $18^\circ K$ is the highest one known.

SOME intermetallic compounds crystallizing with the β -wolfram structure become superconducting, as was first pointed out by Hardy and Hulm.¹ In particular one of these, V_3Si , showed a remarkably high transition temperature between $16.9^\circ K$ and $17.1^\circ K$. These authors made various attempts to raise this temperature by introducing a third component but were not successful.

The β -wolfram structure is a very peculiar structure with rather varying interatomic distances,² a fact which may render the addition of a third component rather difficult. It seemed therefore more favorable to look for another β -W compound with a large volume and a favorable electron/atom ratio³ in order to raise the superconducting transition temperature. There is very little known about the systematic occurrence of intermetallic compounds in this β -W structure. The fact that thus far no niobium compounds have been reported seemed therefore not significant.

It was expected that in the Nb-Sn and Ta-Sn this crystal form would be found, an assumption which was verified. We have determined that Nb_3Sn and Ta_3Sn both crystallize in a β -W structure with a lattice constant of about 5.3Å. The Ta_3Sn was measured in the apparatus previously described,⁴ and became superconducting near $6^\circ K$. The transition temperature of the Nb_3Sn was determined by immersing the sample surrounded by a copper coil in liquid hydrogen. The self-inductance of the coil was measured on a General Radio Model 650A Bridge at 1 kc/sec as the sample was slowly cooled. Figure 1 shows the results for two different samples made under somewhat different conditions which were cooled from $18.5^\circ K$ to $17.5^\circ K$ during a period of about 30 minutes. The sharpness of the transition together with the reproducibility between samples indicates that these samples are indeed well-defined compounds. The onset of superconductivity at

$18.05^\circ K \pm 0.1^\circ$ is determined by extrapolating the line of steepest slope to the high temperature line. Temperatures were measured by a copper constantan thermocouple secured to the measuring coil and independently checked with the vapor pressure of hydrogen.

APPENDIX

While the synthesis of an intermetallic compound is generally a rather straightforward process, it may be necessary to describe briefly the formation of these

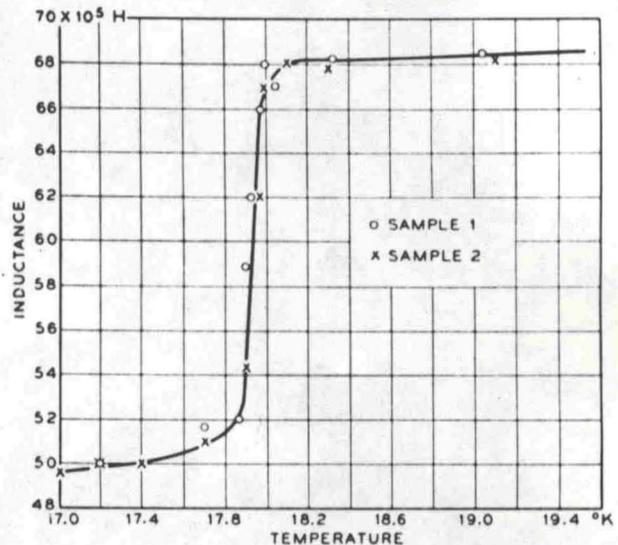


FIG. 1. Variation of susceptibility with temperature of Nb_3Sn .

compounds. No reference to Nb-Sn or Ta-Sn was found in the literature. The melting point of niobium is nearly 400° above the boiling point of tin, and an arc furnace is therefore out of place. A complete reaction can, however, easily be obtained by having molten tin run over Nb or Ta powder in a closed-off quartz tube at $1200^\circ C$. Nb_3Sn and Ta_3Sn seem to be formed by a peritectic reaction between $1200^\circ C$ and $1550^\circ C$.

¹ G. Hardy and J. K. Hulm, Phys. Rev. **89**, 884 (1953).

² H. I. Wallbaum, Z. Metallkunde **31**, 362 (1939).

³ B. T. Matthias, Phys. Rev. **92**, 874 (1953).

⁴ B. T. Matthias and J. K. Hulm, Phys. Rev. **87**, 799 (1952).